

Li-ion Battery High-energy Silicon Anode Innovation & Patent Review

Table of Contents (in parentheses: date of latest version)

<u>Executive Summary</u> (2024-09-16)	3
<u>About the Author</u>	5
<u>Introduction</u> (2024-09-30)	5
• <u>Focus of this Review</u>	5
• <u>Li-ion Battery Cell Components</u>	6
• <u>Si-based Electrodes for Cells with Liquid, Semi-solid & All-solid Electrolytes – Opportunities, State-of-upscaling, Challenges, Competitive Threats</u>	7
<u>Technology Decision Trees & Discussion</u> (2024-09-20)	12
• <u>Main Categories</u>	12
• <u>Nano-Si (Synthetic Processes)</u>	14
• <u>Heteroelements Incorporated into Si</u>	15
• <u>Nano-Si (Surface Treatments)</u>	16
• <u>Coating of Carbon with Si (Monosilane Deposition)</u>	18
• <u>Si-carbon Composites – Dry or Wet Mixed Si / C – Synthetic Processes – Core</u>	20
• <u>Si-carbon Composites – Dry or Wet Mixed Si / C – Precursors (Other Than Si, Binders, Dispersants)</u>	21
• <u>Si-carbon Composites – Dry or Wet Mixed Si / C – Binders / Dispersants</u>	21
• <u>Si-carbon Composites – Dry or Wet Mixed Si / C – Coatings</u>	22
• <u>SiO_x (0.25 ≤ X ≤ 1) (Synthetic Processes)</u>	22
• <u>Incorporation of Heteroelements into SiO_x (0.25 ≤ X ≤ 1)</u>	23
• <u>Incorporation of Li into SiO_x (0.25 ≤ X ≤ 1)</u>	23
• <u>SiO_x (0.25 ≤ X ≤ 1) (Coatings)</u>	24
• <u>Functionalization of Carbon-coated SiO_x (0.25 ≤ X ≤ 1)</u>	24
• <u>Additives for Negative Electrodes</u>	25
• <u>Binders for Negative Electrodes</u>	26
• <u>High-energy Electrode Designs & Fabrication Methods</u>	27
• <u>Excerpt from 'Solid-state Li-ion Battery Innovation & Patent Review' Negative Electrode Materials</u>	29
<u>Predictions (5-10 Year Time Frame)</u> (2024-09-16)	31
<u>AI-based Identification of Commercially Relevant Patents</u> (2024-08-21)	32
<u>Assessment of Companies</u>	39
• <u>Advano – USA</u> (2024-09-20)	39
• <u>Alkegen – USA</u> (2024-07-30)	44
• <u>Amprius – USA</u> (2024-02-21)	49
• <u>Aspen Aerogels – USA</u> (2024-06-30)	57
• <u>BTR – China</u> (2024-04-08)	62

• BYD – China (2024-05-17)	67
• Contemporary Amperex Technology Limited (CATL) – China (2024-08-28)	71
• Daejoo Electronic Materials – South Korea (2024-06-30)	77
• E-magy – Netherlands (2024-06-30)	82
• Enevale – USA (2024-06-30)	86
• Enovix – USA (2024-03-14)	92
• Group14 Technologies / Cellforce Group – USA / Germany (2025-02-07)	99
• Ionic Mineral Technologies – USA (2024-09-20)	106
• Ionobell – USA (2024-07-30)	109
• LeydenJar Technologies – Netherlands (2024-05-17)	113
• LG Energy Solution / LG Chemical – South Korea (2024-06-30)	119
• Nanoramic Laboratories – USA (2024-06-30)	127
• Neo Battery Materials – Canada (2024-07-30)	131
• Nexeon / Wacker Chemie – UK / Germany (2025-02-07)	134
• OneD Battery Sciences – USA (2024-04-15)	141
• Panasonic – Japan (2024-05-17)	149
• Posco – South Korea (2024-02-21)	154
• Putailai / Zichen – China (2024-04-08)	159
• Resonac – Japan (2024-05-17)	163
• Samsung – South Korea (2024-05-17)	168
• Shanshan – China (2024-03-14)	173
• Shin-Etsu – Japan (2024-03-14)	179
• Shinzoom – China (2024-05-17)	188
• Sila Nanotechnologies – USA (2024-02-16)	192
• StoreDot – Israel (2024-04-05)	201
• Tesla – USA (2024-06-30)	206
• Toyota – Japan (2024-05-17)	211
• Umicore – Belgium (2024-08-30)	218
• Zhide – China (2024-04-15)	222
Competing Technology Approach –	
Deep Dive – Interfaces: Li Metal Electrodes – Polymer-based Electrolytes (2024-09-03)	227
• Introduction	227
• Ion-conductive Polymers – Estimate of the Current State of the Art	227
• Reducing the Need for Electrochemical Stability of Polymer Electrolytes	230
• Incorporation of Non-conducting Porous Polymer Films	233
• A Four-track Product Development Approach	234
• Cell Failure Root Causes That Cannot Easily Be Identified at Lab Scale	237
• Conclusion	239
Deep Dive – Interfaces: Si-based Electrodes – Sulfide Electrolytes (2024-12-11)	241
• Introduction	241
• 'Decision Maze' Towards Product Launch	242
• Academic Findings on Si-sulfide Interface Reactions	242
• Parasitic Reactions of Carbon Additives in Si-based Negative Electrodes	244
• Electronic Conductivity of Si and Si-Li Alloys in Carbon-free Negative Electrodes	244
• Role of Porosity and Tortuosity in Si-based Negative Electrodes	244

• Active Material Optimization for Dry Processing	248
• Reconsidering the ‘Decision Maze’ – Under-explored Approaches	248
• Conclusion	251
• Summaries of Patent Families Discussed in ‘Decision Maze’	252
Deep Dive – Interfaces: Si-based Electrodes – Polymer & Oxide Electrolytes (2025-02-03)	259
• Introduction	259
• ‘Semi-solid’ Electrolytes & Si-based Active Materials – A Pair of ‘Imperfect’ Materials That Enabled Above-average Progress to Market Launches	259
• Estimate of Current State of the Art	260
• ‘Decision Maze’ Towards Product Launch	260
• Hypothesis- and Data-driven Interface Design	267
• Impact of the Negative Electrode / Electrolyte Interface on Cell Performance	268
• Feasibility of Data-driven Screening Approaches	268
• Which Si-based Active Materials Have Been ‘Under-explored’ in Combination with Oxide and / or Polymer-based Electrolytes?	269
• The Lowest-Cost Solution Wins if Performance & Safety Are Almost Equal	270
AI Patent Analysis Methodology	270
List of Abbreviations	270
Disclaimer	272

Appendix: Example of Triweekly Patent Update

About the Author

Pirmin Ulmann built b-science.net together with co-founders into a company with subscribers across America, Asia and Europe, ranging from startups to Fortune Global 500 companies, plus academic / government-affiliated organizations and investors. He obtained a diploma in chemistry from ETH Zurich (Switzerland) in 2004 and a PhD from Northwestern University (USA) in 2009. Thereafter, he was a JSPS Foreign Fellow in an ERATO academic-industrial project at the University of Tokyo (Japan). From 2010 to 2016, while working at a major battery materials manufacturer in Switzerland, he was a co-inventor of 7 patent families related to lithium-ion batteries. He also was in charge of a collaboration with the Paul Scherrer Institute. He holds the credential Stanford Certified Project Manager (SCPM) and has co-authored scientific articles with >2,000 citations.

Introduction

Focus of this Review

This review is designed for R&D, IP, product management, business development and VC decision makers involved with the prospective launch of novel Si-based negative electrode materials and corresponding Li-ion battery cells. Since 35-45% of high-tech product launches

failed as of 2022, the employment of tools that improve decision-making in this domain is highly advisable. Several of the key players discussed in company chapters below have purchased b-science.net subscriptions.

Based on a unique AI-supported approach, this review highlights commercially relevant technical and patent information that has been identified among the >100k battery patent documents published every year. Divergent technical decisions are visualized and discussed, which have been taken by key commercial players.

Patents are classified according to these categories:

- A) Active materials – chemical composition
- B) Active materials – nano- & micro-architectures, composites
- C) Active materials – surfaces & coatings
- D) Large scale manufacturing, reliability
- E1) Negative electrodes for cells with liquid carbonate-based electrolytes
- E2) Negative electrodes for cells with semi-solid electrolytes
- E3) Negative electrodes for cells with all-solid electrolytes

Patent portfolios are compared to public technical statements at conferences and in news reports about the characteristics of next-generation products and up-scaling timelines.

For tailored patent searches with prospective commercial relevance scoring, the AI models used for preparation of this review are available to users on b-science.net.

Si-based Electrodes for Cells with Liquid, Semi-solid & All-solid Electrolytes – Opportunities, State-of-upscaling, Challenges, Competitive Threats

Table 1: commercialization phase of companies that develop or deploy Si-based active materials

Company	Country	Probable Si Formation Approach	Commercialization Phase (According to Publicly Available Information)
<u>Sila Nanotechnologies</u>	USA	Monosilane CVD deposition on carbon	<u>Construction of gigafactory (supply of Panasonic & Mercedes-Benz)</u>

34 companies are listed in the full review.

Technology Decision Trees & Discussion

The technology decision trees below should not be regarded as comprehensive, because the selection of a limited number of ‘commercially relevant’ patents among the ≈3k battery patents published each week involves substantial ‘tree trimming’ (of branches that would be commercially relevant in a more narrow, ‘zoomed-in’ category).

However, the technology decision trees below are designed to serve as a source of inspiration for novel inventions and for the identification of technical approaches that have been ‘under-explored’ thus far, at a suitable ‘zoom level’.


The coloring scheme below is used for Figures 2-19. As compared to the 2022 review edition:

- **Added / changed branches are displayed in red.**
- Unchanged branches are displayed in black.
- Branches for which the underlying patent discussion has been dropped from the current review edition are displayed in gray. These patent discussions are available in the 2022 review edition.

Since the 2022 edition of this review was published, several synthetic approaches to nano-Si have attracted substantially increased commercial interest (Figure 3):

- **CVD (monosilane) deposition**, including on carbon scaffolds (further discussed in relation to [Figure 6](#)), on Si nano- or microparticles ([BTR](#), [LG Energy Solution](#)), on Cu current collector foils ([Amprius](#), [LeydenJar](#)), on various substrates ([OneD Battery Sciences](#)).
Unique capability: synthesis of various nanostructures with Si domain size of <50 nm and extremely limited oversize structures.
Leap of faith: the above structures and sufficient corresponding cell performance can only be obtained through monosilane CVD deposition, not through low-cost modification of low-cost metallurgical Si precursors.
With regards to [Amprius](#) & [LeydenJar](#), the leap of faith further includes the assumption that Si deposition can be carried out fast enough (ideally >100 m/min, if EV applications are to be targeted) to justify the employment of a roll-to-roll Si deposition process on current collector foils.

Figure 3: technology decision tree – nano-Si (synthetic processes)

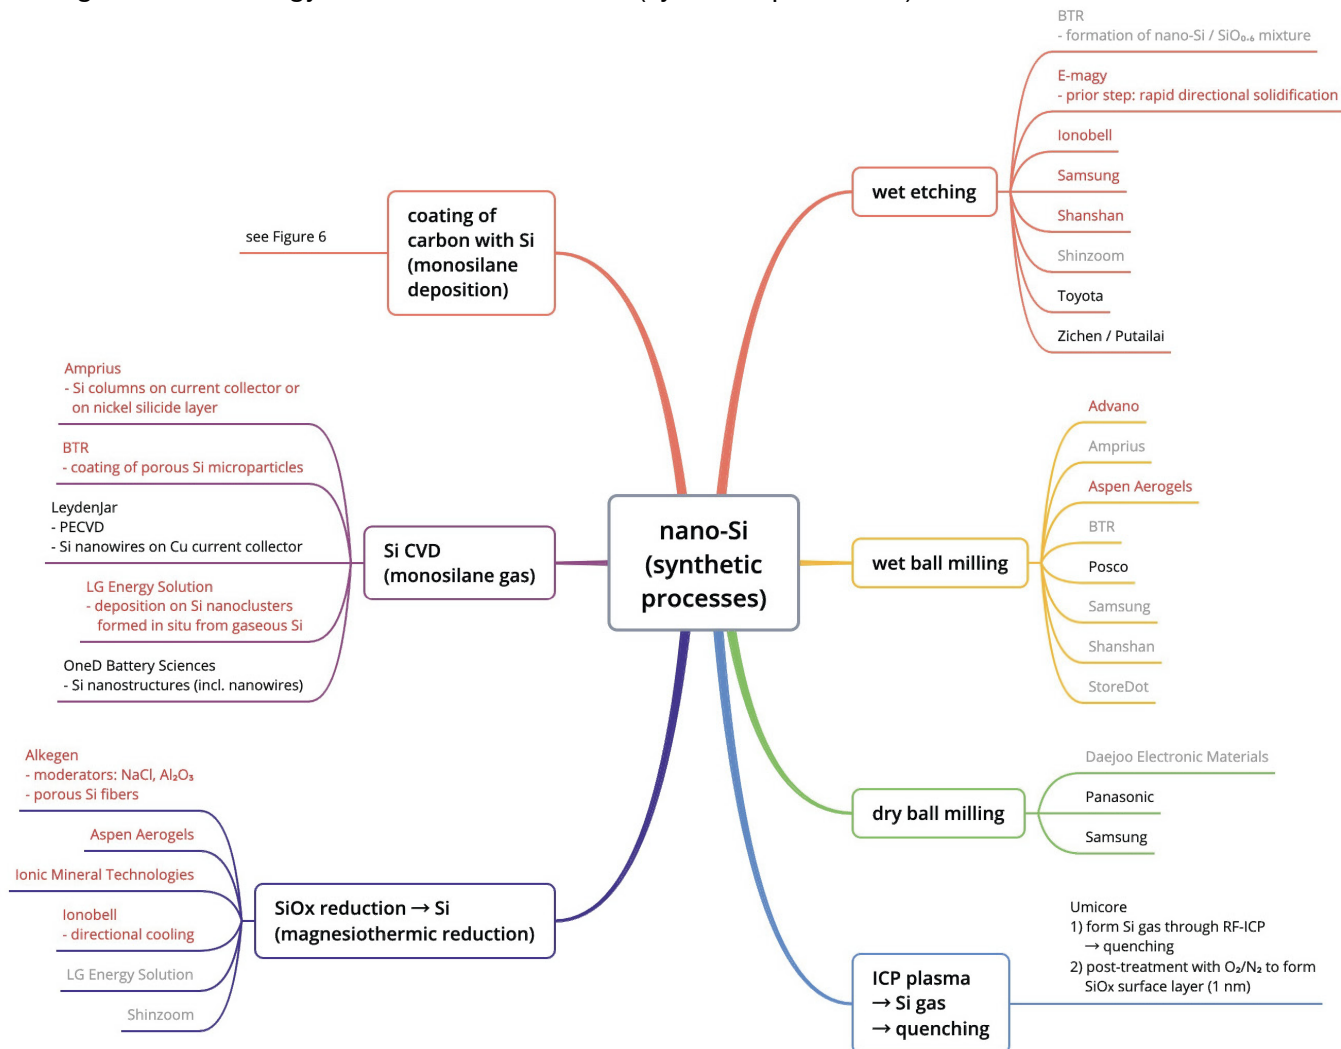

17 additional decision trees & further discussions are included in the full review.

AI-based Identification of Commercially Relevant Patents

b-science.net has developed a supervised AI methodology to assess the commercial relevance of patents, combined with an automatic translation framework that makes sure Non-English patents are identified. With this approach, we comprehensively identify & classify patents by companies active in commercial R&D on Li-ion battery negative electrodes.

Assessment of Companies

Key commercially relevant patent filings and public technical statements are discussed in the company chapters below, which results in a projection by the author in the form of industrially plausible manufacturing processes that could allow for the synthesis of novel Si-based active materials (prospective active material characteristics are also listed).

In the following chapters, patent families that were not covered in the prior review edition (February 2022) are shown in red.

Author comments are displayed in maroon.

Example of Company Chapter – Umicore – Belgium

Organization profile

Umicore (<http://www.umicore.com/>) is a market-leading supplier of NMC cathode materials that is also active in transition metal recycling.

Unique capability: Si-carbon composite formation process that involves RF-ICP (radio frequency inductively coupled plasma).

Leap of faith: manufacturing can be upscaled quickly and cost-effectively as claimed (presumably involving RF-ICP-based Si volatilization and formation of Si nanoparticles), achieving a sufficiently small Si particle size to achieve sufficient cycling stability. To the extent of the author's knowledge, RF-ICP is not used at current to commercially produce materials used in the Li-ion battery industry. Thermal plasma gasification plants with >500 tons per day capacity have been built to treat municipal solid waste, which might be considered as industrial scale validation of a related process in a comparably cost-sensitive application (waste disposal).


Key differences as compared to 2022 review edition

- Umicore announced its plans “to be the 1st European silicon anode player at scale”.
- According to a patent portfolio analysis, Umicore might target an anode material with well-rounded performance by incorporating RF-ICP volatilization and deposition of Si nanoparticles into a sulfur-containing carbon matrix (no use of monosilane gas).

Possible composition of future silicon-based negative electrode active materials (for liquid carbonate-based, semi-solid or solid electrolyte cells)

- According to a SEM image from a presentation at The Battery Show Europe 2023 (slide 11), the active material appears to consist of microparticles that contain homogeneously mixed Si-carbon nano-domains (without or with a small volume of void space), mixed with graphite flakes.
- BET SSA of 4.8 m²/g (might be further reduced by applying a carbon or polymer coating, although no recent patent literature was identified in this regard).
- Si / O / S / C mass ratio of 40.1 : 3.4 : 0.109 : 56.4.
- Particle size distribution of Si nanoparticles: dNS₁₀ = 59 nm, dNS₅₀ = 114 nm, dNS₉₀ = 192 nm. Presumably, the evolution towards higher capacity and Si content in Si-carbon composites goes along with further reducing Si nanoparticle size.
- Oxygen content of Si nanoparticles: 7.8 mass%.

Figure U1: projected manufacturing process for Si-carbon composite active material by Umicore (red: changes vs. 2022 review edition, up-scaled implementation may vary)

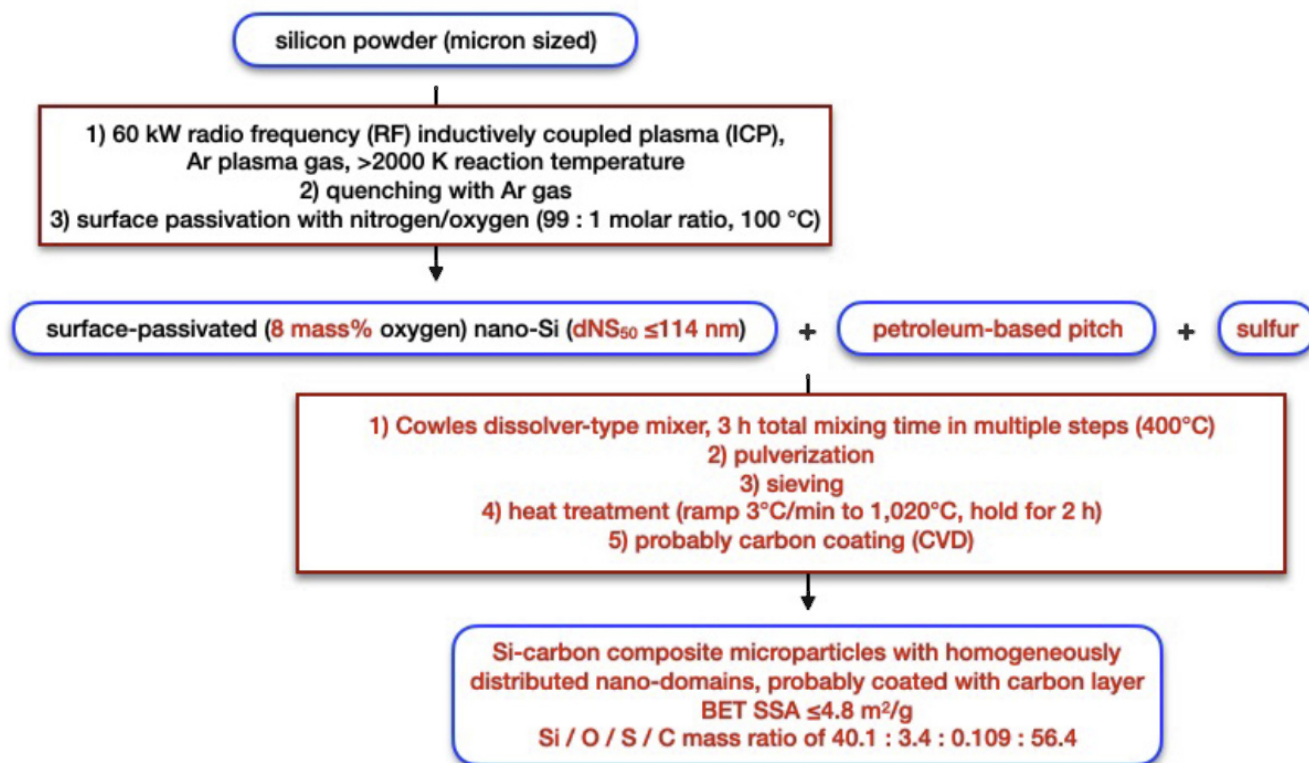

Public technical statements & reports

At The Battery Show Europe in June 2023, Jean-Sébastien Bridel (Anode Program Manager) stated:

- Their target is to become the first European silicon anode player at scale.
- By 2029, Si-carbon composite active materials will supersede SiO_x in terms of volumes deployed in cells.
- They are in the process of launching Si-carbon composite materials that are not produced from silane gas.
- In terms of the IP landscape, freedom of operation is higher in the area of Si-carbon composites as compared to SiO_x (control of key IP by a few major players).
- They have an anode-related IP portfolio with 39 patent families (over 200 patents).
- Several EV customers (battery makers and OEMs) confirmed the favorable and well-balanced performance of their Si-carbon active material (active material is being delivered to these customers at ton-scale).
- They achieve the best costs (USD/kWh) upon use of abundant raw materials, and can scale up their process based on easy equipment access.
- Their UM1500XX and UM1650XX grades exhibit capacities of 1,500-1,650 mAh/g.
- Their UM1300MG grade exhibits a capacity of ≈1,300 mAh/g and a capacity retention of ≈87% after 1,000 cycles (1 C charge / discharge, NMC811-based positive electrodes). An SEM image after cycling ([slide 11](#)) suggests that Si-carbon composite microparticles remained intact, inside which Si and carbon nanodomains appear to be homogeneously distributed. Favorable stability due to an engineered Si-carbon interface and Si volume change compensation by the carbon matrix are claimed.
- Their Si material does not undergo a phase change during cycling.
- No pre-lithiation is necessary.

General patent portfolio characteristics

7 new patent families by Umicore have been published since 2022 that are related to high-energy Li-ion battery anodes (without lithium metal anodes). 3 new lithium metal anode patent families have been published since 2022.

Example from the patent portfolio

Active materials – A) chemical composition; B) nano- & micro-architectures, composites; C) surfaces & coatings

- **Process in Figure U1 – [A POWDER FOR USE IN THE NEGATIVE ELECTRODE OF A BATTERY, A METHOD FOR PREPARING SUCH A POWDER AND A BATTERY COMPRISING SUCH A POWDER](#) (Google, published in 2023, covered in patent update):**

micron-sized silicon powder was injected into an RF-ICP (200 g/h, 60 kW, reaction temperature >2,000 K), which resulted in complete vaporization, followed by deposition in an argon gas flow (20 Nm³/h, <1,600 K), followed by a passivation step (100°C, 5 min, 100 L/h, N₂/O₂ = 99 : 1 molar ratio).

The resulting material exhibits a BET SSA of 81 m²/g, an oxygen content of 7.8 mass%, and a number-based particle distribution of dNS₁₀ = 59 nm, dNS₅₀ = 114 nm, dNS₉₀ = 192 nm.

This powder was blended with petroleum-based pitch powder and sulfur (100 : 200 : 0.45 by mass, 400°C, under nitrogen, Cowles dissolver-type mixer, 3 h total mixing time in multiple steps), followed by pulverization, sieving, a heat treatment (heat at 3°C/min to 1,020°C, hold for 2 h), sieving.

The resulting material exhibits a BET SSA of 4.8 m²/g, an Si / O / S / C mass ratio of 40.1 : 3.4 : 0.109 : 56.4 and a first cycle discharge capacity of 1,342 mAh/g. Negative electrodes in which graphite active material was additionally included exhibit a 1st cycle discharge capacity of 847 mAh/g, a coulombic efficiency of 90.73%, and an average coulombic efficiency in cycles 5-50 of 99.79% (half-cells), as compared to 846 mAh/g, 89.31% and 99.64% for a comparative example with an active material that was prepared without sulfur. Additional, earlier patent families follow a similar RF-ICP-based approach to obtain Si nanoparticles, while relying on different carbon precursors that apparently led to worse electrochemical performance as compared to the approach discussed above:

- [WO 2022074031 A1 \(Google\)](#): use of petroleum-based pitch without sulfur.

- [WO 2023275223 A1 \(Google\)](#): use of phenol-formaldehyde resin without sulfur.

This work illustrates how the presence of a minor amount of sulfur improves the electrochemical characteristics of Si-carbon composite materials.

This patent filing could plausibly cover the active material presented at Battery Show Europe 2023 ([see above](#)), although there is no absolute guarantee that this is the case.

Key earlier patent that might correspond to prospective commercial products

Active materials – B) nano- & micro-architectures, composites; C) surfaces & coatings

- **Process in Figure U1 – A POWDER FOR USE IN THE NEGATIVE ELECTRODE OF A BATTERY, A METHOD FOR PREPARING SUCH A POWDER AND A BATTERY COMPRISING SUCH A POWDER** (Google, published in 2021, covered in patent update, **granted by CN**): a sub-micron silicon powder (d₉₀ : 205 nm) was synthesized by applying 60 kW RF-ICP to a micron-sized silicon powder (argon as plasma and quenching gas, >2,000 K reaction temperature). In a passivation step, the powder was treated with a nitrogen / oxygen mixture (1 mol% oxygen, 100°C). This powder was mixed with zirconium powder (average particle size 50-100 nm) and ball-milled under argon, followed by a heat treatment (773 K, 2 h, dry argon, <3 ppm water, <3 ppm oxygen). Oxygen content in product particles: 8.7 mass%, Zr content: 0.1-5 mass%, BET SSA: about 83 m²/g. Using

an XPS analysis, the oxidation state of Zr near the surface (up to 10 nm depth) was confirmed to be +IV. It is unexpected that a 1st cycle efficiency of 88.15% is reported in consideration of the high surface area of the Si particles and that 25 mass% carbon black were used in negative electrodes along with 2 mass% carbon fibers and 25 mass% PVDF.

This work suggests that a ZrO_2 coating of Si nanoparticles results in a favorable electrolyte / electrode interface in cells.

AI Patent Analysis Methodology

The patent information source for this review is the European Patent Office (EPO), which covers patent filings from more than 100 patent offices around the world. >2.8M patent documents are included in the b-science.net database published since 1980, which either contain the words 'battery' or 'batteries' in the title or abstract, or were assigned to one of the energy storage-related CPC (cooperative patent classification) or IPC (international patent classification) codes: H01M (batteries & fuel cells) or H01G (capacitors). An AI model was defined for commercially relevant negative electrodes of Li-ion batteries (without Li metal electrodes). Patent documents were grouped into patent families and scored with the corresponding AI model. An AI relevancy score cutoff value of 40 was applied (100: very relevant, 0: not relevant). Only private / commercial companies are included in the statistics.

Appendix: Example of Triweekly Patent Update

Version: 2024-07-30 ([Excel Patent List](#))

JAGGED ELECTROCHEMICALLY-ACTIVE COMPOSITE PARTICLES FOR LITHIUM-ION BATTERIES ([Google](#))

Applicant: SILA NANOTECHNOLOGIES / WO 2024145561 A1

Cuboid Si-carbon composite active materials were prepared as shown in the SEM images below (top: Si-carbon material powder, bottom: Si-carbon / graphite-based electrode cross-section).




Negative electrode types A (≈ 600 mAh/g capacity) and B ($\approx 1,000$ mAh/g capacity) were prepared upon mixing with graphite, polyacrylic acid (PAA, ≈ 4 mass%) and single-walled carbon nanotubes (SWCNT, 0.05 mass%).

While details for the whole manufacturing process were not identified, a detailed analysis of the impact of ball milling as compared to jet milling is included as shown in the graph below, which

illustrates that jet milling results in a more narrow particle size distribution.

Extensive comparative pouch cell cycling stability data illustrates that an Si-carbon composite material with a narrow particle size distribution and a BET specific surface area of 3.7 m²/g exhibits the highest cycle life (2,276 cycles until 80% capacity retention, NMC811-based positive electrodes, negative electrode areal capacity: ≈4.1 mAh/cm², 2 C charge to 4.0 V, then 1 C charge to 4.2 V, then 0.05 C charge, 1 C discharge).

SPAN: (D90 - D10) / D50

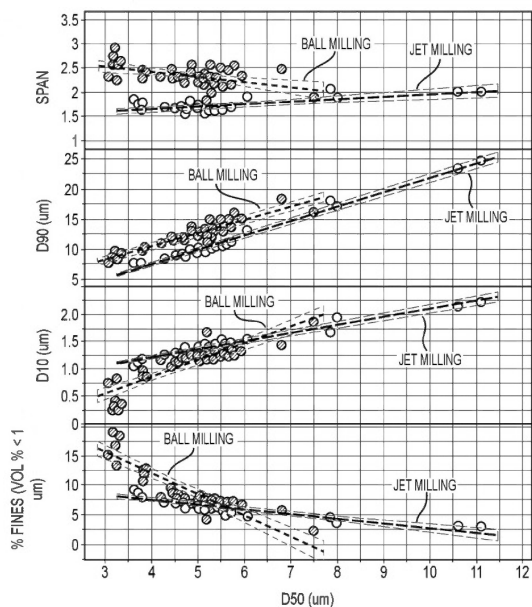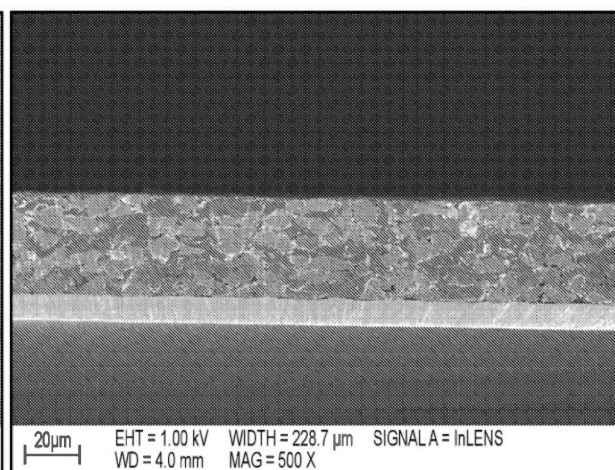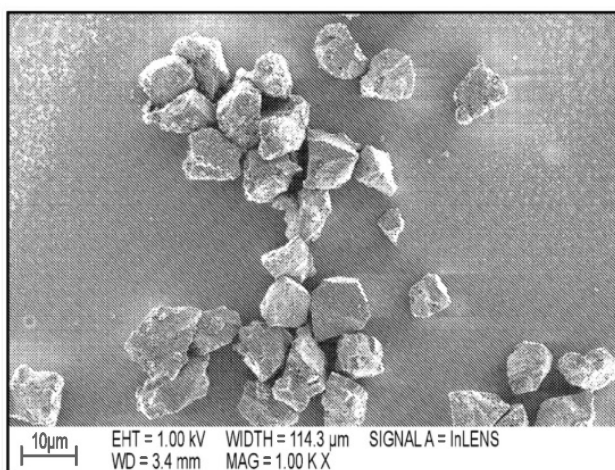

COMPOSITE PARTICLE SAMPLE NO.	ELECTRODE TYPE	PSD (BROAD OR NARROW)	D10 (µm)	D50 (µm)	D90 (µm)	D99 (µm)	SPAN	FWHM (µm)	D10/D50	BET SSA (m ² /g)	BLEND CAPACITY (mAh/g)	COATING DENSITY (g/cm ³)	CYCLE LIFE (N80) (CYCLES)
1	A	BROAD	1.1	3.65	8.49	12.38	2.06	8.5	30%	14.3	600	1.53	973
1	B	BROAD	1.1	3.65	8.49	12.38	2.06	8.5	30%	14.3	1000	1.27	530
2	A	BROAD	1.34	5.03	11.21	15.54	1.92	8.5	27%	9.8	600	1.65	1203
2	B	BROAD	1.34	5.03	11.21	15.54	1.92	8.5	27%	9.8	1000	1.33	701
3	A	BROAD	2.11	8.02	17.44	24.56	1.9	16.0	26%	6.9	600	1.67	1380
3	B	BROAD	2.11	8.02	17.44	24.56	1.9	16.0	26%	6.9	1000	1.35	840
4	A	BROAD	2.58	10.16	22.6	32.86	1.97	23.0	25%	6.3	600	1.76	1254
4	B	BROAD	2.58	10.16	22.6	32.86	1.97	23.0	25%	6.3	1000	1.38	762
5	A	BROAD	3.01	13.31	30.48	44.12	2.07	25.0	23%	5.8	600	1.71	1106
5	B	BROAD	3.01	13.31	30.48	44.12	2.07	25.0	23%	5.8	1000	1.36	709
6	A	NARROW	0.9	2.69	5.41	7.56	1.58	3.0	33%	14.5	600	1.65	963
6	B	NARROW	0.9	2.69	5.41	7.56	1.58	3.0	33%	14.5	1000	1.32	643
7	A	NARROW	4.69	6.77	9.67	12.11	0.74	5.5	69%	6.7	600	1.59	2251
7	B	NARROW	4.69	6.77	9.67	12.11	0.74	5.5	69%	6.7	1000	1.38	1071
8	A	NARROW	7.05	9.82	13.68	16.92	0.67	6.0	72%	3.7	600	1.63	2276
8	B	NARROW	7.05	9.82	13.68	16.92	0.67	6.0	72%	3.7	1000	1.38	1280
9	A	NARROW	11.61	16.8	23.96	30.62	0.74	8.0	69%	2.8	600	1.64	1919
9	B	NARROW	11.61	16.8	23.96	30.62	0.74	8.0	69%	2.8	1000	1.42	846

This work tends to suggest that Sila Nanotechnologies shifted its focus from spherical to cuboid Si-carbon composite particles with narrow particle size and a BET specific surface area of ≈3.7 m²/g, presumably obtained through jet milling prior to applying the carbon coating.

Presumably, improved longevity was obtained because cuboid particles less easily lose particle-particle contact upon volume expansion (face-to-face contact by cuboid particles as opposed to point-to-point contact between spherical particles).

In addition, high volumetric energy densities can also be achieved with cuboid active material particles (less void space as compared to spherical particles with narrow particle size distribution).


A porous silicon material and its preparation method and use (Google)

Applicant: Hunan Shinzoom Technology / CN 118255357 A

Nickel-silicon alloy powder (D50: 8 μm , 20 mass% Si) was treated with CO gas in a rotary nickel carbonyl synthesis reactor with a screw conveyor (countercurrent CO gas flow, 65°C, 0.08 MPa, 20 h), which resulted in nickel carbonyl gas and a porous Si material.

The porous silicon material was passivated with an oxygen / argon gas mixture (5 : 95 by volume, see SEM image below).

No electrochemical data is included in the patent application.

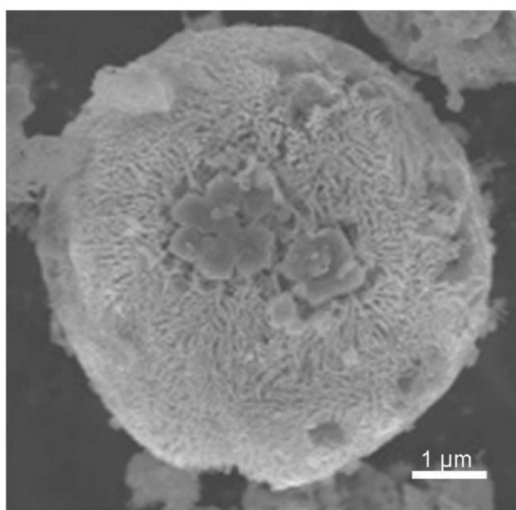

This process could allow for the avoidance of comparably hazardous aqueous HF-etching process steps.

Considering that nickel carbonyl gas is [carcinogenic](#), advantages and disadvantages as compared to HF-etching processes have to be carefully considered.

Nickel carbonate gas can be recycled back to nickel metal and CO gas using a [well-known industrial process](#) (at 220-250°C).

A silicon-carbon composite negative electrode material and its preparation method and use (Google)

Applicant: Hunan Shinzoom Technology / CN 118248843 A

Porous carbon was CVD (chemical vapor deposition)-treated with a SiH₄ (monosilane) / PH₃ (phosphine) / H₂ (hydrogen) gas mixture (600°C, 10 h, gas volume ratio not disclosed), followed by another CVD treatment (700°C, 8 h, methane / argon, gas volume ratio not disclosed). It is argued that P-Si-P bonds are formed because PH₃ is used as opposed to elemental P.

In half-cells, a discharge capacity of 1,701 mAh/g and a first cycle efficiency of 91.3% were measured, as compared to 1,656 mAh/g and 87.9% for a P-free comparative material.

In full cells (LiCoO₂-based positive electrodes), a capacity retention of 92.8% was measured (5 C charge / discharge), as compared to 70.0% for a P-free comparative material.

This work suggests that P-doping (PH₃ as CVD-precursor) results in substantially improved longevity upon fast charge / discharge.

Disclaimer

All warranties and liabilities on the part of b-science.net GmbH (LLC) and its affiliates are excluded, including, without limitation, guarantees as to fitness for a specific purpose, non-infringement, accuracy or completeness. Please check our [Terms & Conditions](#) and [Privacy Policy](#), which apply to this document.

THIS SERVICE MAY CONTAIN TRANSLATIONS POWERED BY GOOGLE. GOOGLE DISCLAIMS ALL WARRANTIES RELATED TO THE TRANSLATIONS, EXPRESS OR IMPLIED, INCLUDING ANY WARRANTIES OF ACCURACY, RELIABILITY, AND ANY IMPLIED WARRANTIES OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE AND NONINFRINGEMENT.